




European Regional Product Data


# Calcined and Reactive Aluminas for Refractories



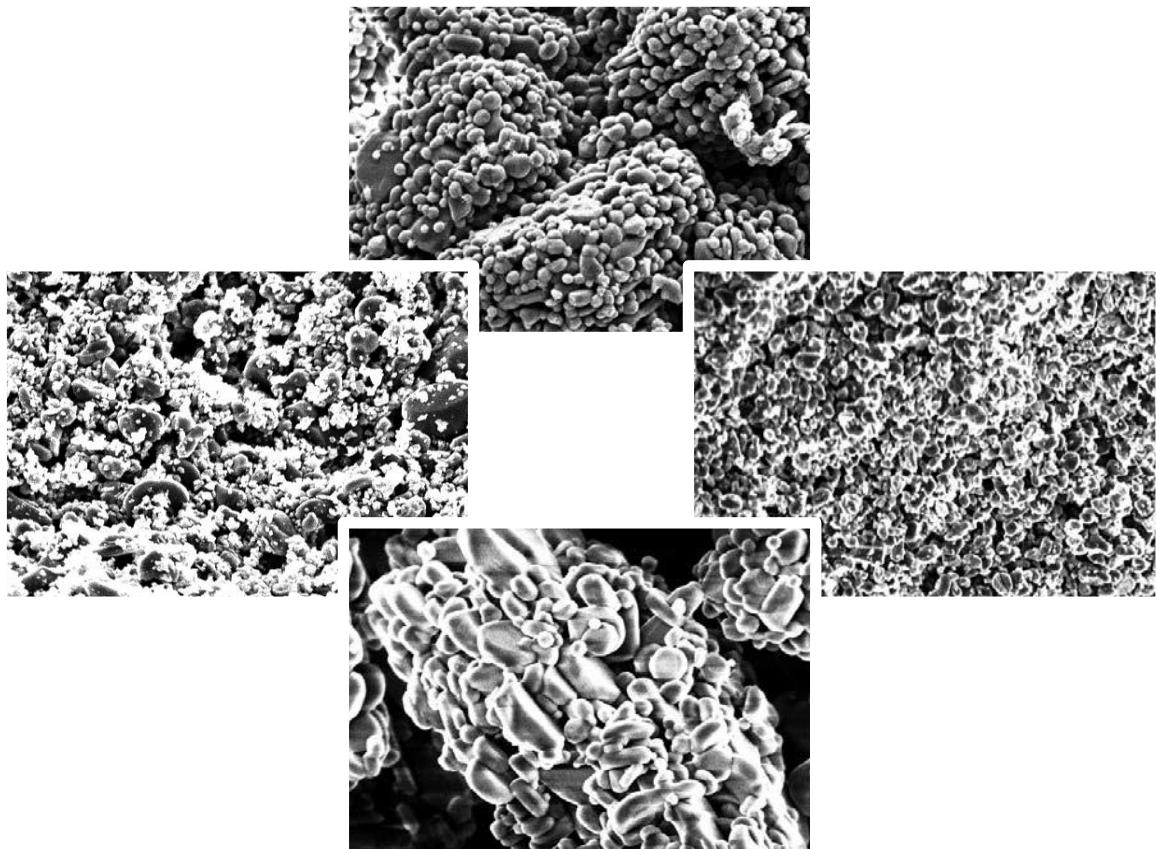

## Ground Calcined Aluminas for Refractories

ground		CT 9 G											
Properties / method	Unit	typical	Min	Max	typical	Min	Max	typical	Min	Max	typical	Min	Max
Specific Surface Area / BET	[m <sup>2</sup> /g]	0.70											
Particle Size / sieve > 63 µm	[%]	1.0		3.0									
Chemical Analysis													
Al <sub>2</sub> O <sub>3</sub>	[%]	99.5											
Na <sub>2</sub> O	[%]	0.15		0.30									
Fe <sub>2</sub> O <sub>3</sub>	[%]	0.04		0.06									
SiO <sub>2</sub>	[%]	0.03		0.06									
fineground		CT 9 FG			CT 19 FG			CT 800 FG					
Specific Surface Area / BET	[m <sup>2</sup> /g]	0.80			0.60	0.40	0.80	0.90	0.70	1.20			
Particle Size / D50 Cilas	[µm]	3.5	2.0	7.0	5.5	4.0	7.5	3.5	2.5	5.0			
Particle Size / wet sieve > 45 µm	[%]				1.0		3.0	0.1		3.0			
Particle Size / Cilas > 45 µm	[%]	1.0		3.0									
Water Absorption	[%]	20		22									
Chemical Analysis													
Al <sub>2</sub> O <sub>3</sub>	[%]	99.5			99.8			99.7					
Na <sub>2</sub> O	[%]	0.15		0.30	0.08		0.10	0.12		0.15			
Fe <sub>2</sub> O <sub>3</sub>	[%]	0.04		0.06	0.02		0.04	0.02		0.04			
SiO <sub>2</sub>	[%]	0.03		0.06	0.02		0.05	0.02		0.04			
superground					CT 800 SG			CT 10 SG					
Specific Surface Area / BET	[m <sup>2</sup> /g]						1.0	0.80	1.50	13.0			
Particle Size / D50 Cilas	[µm]						3.4	2.5	4.0	3.0			
Particle Size / wet sieve > 20 µm	[%]									2.0		5.0	
Particle Size / Cilas > 20 µm	[%]						0.1		1.0				
Chemical Analysis													
Al <sub>2</sub> O <sub>3</sub>	[%]						99.7			99.5			
Na <sub>2</sub> O	[%]						0.12		0.15	0.4		0.5	
Fe <sub>2</sub> O <sub>3</sub>	[%]						0.02		0.04	0.03		0.04	
SiO <sub>2</sub>	[%]						0.02		0.04	0.03		0.05	

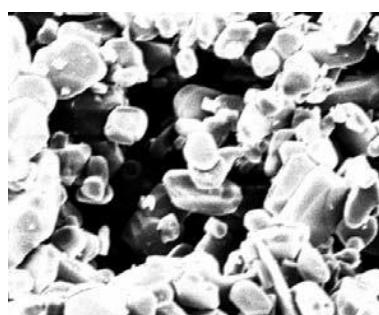

2µm □

CT 19 FG




## Reactive Aluminas for High Performance Refractories


		RG 4000			CTC 20			CTC 22			CL 370		
Properties / method	Unit	typical	Min.	Max.	typical	Min.	Max.	typical	Min.	Max.	typical	Min.	Max.
Specific Surface Area / BET	[m <sup>2</sup> /g]	7.2	6.0	9.5	2.1	1.5	3.0	2.7	2.0	3.5	3.0	2.6	3.4
Particle Size / D50 Cilas	[µm]	0.6	0.4	0.8	1.8	1.4	2.3	1.9	1.4	2.4	2.5	1.8	3.0
Particle Size / D90 Cilas	[µm]	3.0	—	4.0	4.5	—	6.0	5.8	3.9	6.3	7.0	5.0	10.0
Grain Size Distribution		monomodal			monomodal			bimodal			bimodal		
Chemical Analysis													
Al <sub>2</sub> O <sub>3</sub>	[%]	99.8	—	—	99.7	—	—	99.7	—	—	99.7	—	—
Na <sub>2</sub> O	[%]	0.08	—	0.10	0.12	—	0.20	0.12	—	0.20	0.10	—	0.14
Fe <sub>2</sub> O <sub>3</sub>	[%]	0.02	—	0.04	0.03	—	0.05	0.03	—	0.05	0.03	—	0.04
SiO <sub>2</sub>	[%]	0.03	—	0.08	0.03	—	0.08	0.03	—	0.08	0.03	—	0.07
CaO	[%]	0.03	—	—	0.03	—	—	0.03	—	—	0.03	—	—

The typical product properties are based upon the actual averages from production data.


The min/max data show our standard product specification data for these products.

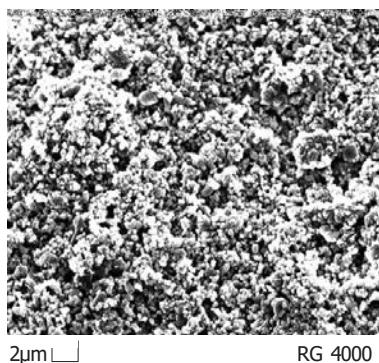

RG 4000

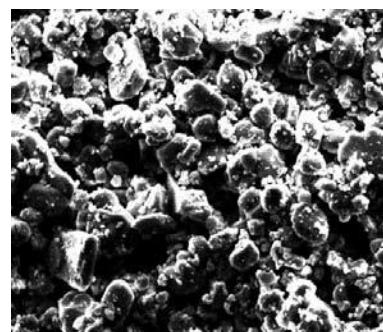

CTC 20

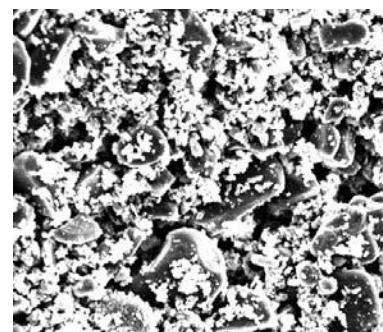

CL 370




## Reactive Aluminas for High Performance Refractories

		CTC 30			CTC 40			CTC 50			CTC 55*		
Properties / method	Unit	typical	min.	max.	typical	min.	max.	typical	min.	max.	typical	min.	max.
Specific Surface Area / BET	[m <sup>2</sup> /g]	3.8	3.0	4.5	4.8	4.0	5.5	4.1	3.7	5.5	3.8	3.5	4.7
Particle Size / D50 Cilas	[µm]	1.5	1.2	1.8	1.2	0.8	1.5	1.5	1.1	1.9	1.6	1.3	1.8
Particle Size / D90 Cilas	[µm]	5.0	4.0	6.0	5.5	4.7	6.8	7.5	6.0	9.0	7.5	6.0	8.5
Grain Size Distribution		multimodal			bimodal			multimodal			multimodal		
Chemical Analysis													
Al <sub>2</sub> O <sub>3</sub>	[%]	99.8			99.8			99.8			91.0		
Na <sub>2</sub> O	[%]	0.08		0.12	0.08		0.12	0.16		0.20	0.10		0.20
Fe <sub>2</sub> O <sub>3</sub>	[%]	0.02			0.03			0.03		0.05	0.08		0.12
SiO <sub>2</sub>	[%]	0.03		0.07	0.03		0.07	0.03		0.10	0.05		0.10
CaO	[%]	0.03			0.03			0.03			0.10		
MgO	[%]										8.00	7.30	9.30


The typical product properties are based upon the actual averages from production data.

The min/max data show our standard product specification data for these products.


\* CTC 55 is a Reactive Alumina/Spinel (MSDS 1000)

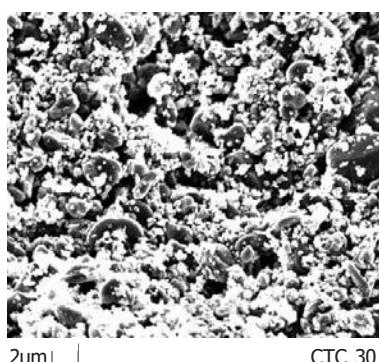

CTC 30

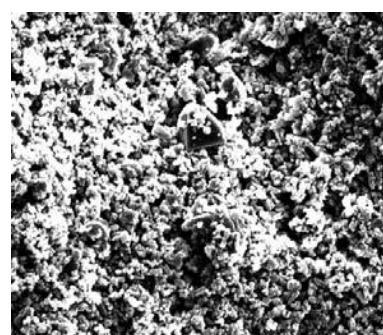

CTC 40

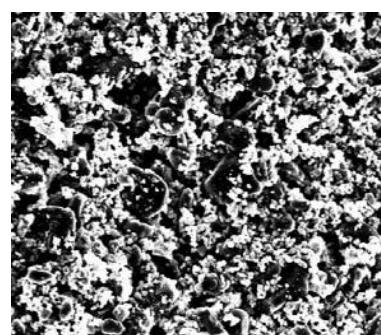

CTC 50



## Calcined Aluminas for Refractories

Due to the excellent high temperature properties of α-Alumina, Calcined Aluminas are used in many refractory applications, both in monolithic and shaped products.

### Product Performance

Depending on the degree of milling and crystal size, Calcined Aluminas serve a variety of different functions in refractory formulations.

Most important are:

- Upgrade product performance by increasing overall Alumina content of these formulations using natural raw materials in order to improve refractoriness and mechanical properties.
- Improve particle packing by increasing the amount of fine particles resulting in better mechanical strength and abrasion resistance.
- Form a matrix of high refractoriness and good thermal shock resistance by reacting with binder components like Calcium Aluminate Cement and / or clays.

## Reactive Aluminas for High Performance Refractories

The fully ground reactive aluminas are specially designed for the production of high performance refractories, where defined particle packing, rheology and consistent placement characteristics are as important as superior physical properties of the final product.

### Product Performance

The highly controlled fine particle size distribution down to the sub-micron range and their excellent sintering reactivity give Reactive Aluminas unique functions in refractory formulations.

Most important are:

- Reduce mixing water of monolithic refractories by helping to optimize particle packing.
- Increase abrasion resistance and mechanical strength by the formation of strong ceramic bonds.
- Increase high temperature mechanical performance by substitution of other superfine materials of lower refractoriness.



## Calcined and Reactive Aluminas for Refractories



### Contacts for sales, technical information and application assistance

Almatis GmbH  
Lyoner Straße 9  
60528 Frankfurt/Germany  
Phone 49 69 957 341 0  
Fax 49 69 957 341 13

[info@almatis.com](mailto:info@almatis.com)  
[www.almatis.com](http://www.almatis.com)

Almatis GmbH  
Giulinistrasse 2  
67065 Ludwigshafen  
Germany  
Phone 49 621 5707 0  
Fax 49 621 5707 130

Almatis B.V.  
Theemsweg 30  
3197KM Botlek RT  
The Netherlands  
Phone 31 181 2701 00  
Fax 31 181 2178 53

Almatis do Brasil Ltda.  
Avenida Jose de Souza  
Campos, 243  
2º Andar – Cambuí  
13025-320 – Campinas,  
SP – Brasil  
Phone 55 19 3515-1400  
Fax 55 19 3515-1410

**SDS 387 SDS 1000**